

Accepted Manuscript

Title: KENAF-POLYPROPYLENE COMPOSITES: EFFECT OF AMPHIPHILIC COUPLING AGENT ON SURFACE PROPERTIES OF FIBRES AND COMPOSITES

Authors: Maya Jacob John, Cornelia Bellmann, Rajesh D. Anandjiwala



PII: S0144-8617(10)00390-5
DOI: doi:10.1016/j.carbpol.2010.05.015
Reference: CARP 4858

To appear in:

Received date: 4-1-2010
Revised date: 23-4-2010
Accepted date: 6-5-2010

Please cite this article as: John, M. J., Bellmann, C., & Anandjiwala, R. D., KENAF-POLYPROPYLENE COMPOSITES: EFFECT OF AMPHIPHILIC COUPLING AGENT ON SURFACE PROPERTIES OF FIBRES AND COMPOSITES, *Carbohydrate Polymers* (2008), doi:10.1016/j.carbpol.2010.05.015

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

1
2 **KENAF-POLYPROPYLENE COMPOSITES: EFFECT OF AMPHIPHILIC**
3 **COUPLING AGENT ON SURFACE PROPERTIES OF FIBRES AND**
4 **COMPOSITES**

5 *Maya Jacob John^{1*}, Cornelia Bellmann³ and Rajesh D. Anandjiwala^{1,2}*

6
7 ¹CSIR Materials Science and Manufacturing, Polymers and Composites Competence Area, P.O. Box
8 1124, Port Elizabeth 6000, South Africa, E-mail: mjohn@csir.co.za

9 ²Department of Textile Science, Faculty of Science, Nelson Mandela Metropolitan University, P.O.
10 Box 1600, Port Elizabeth 6000, South Africa,
11 E-mail: ranandi@csir.co.za, Rajesh.Anandjiwala@nmmu.ac.za

12 ³Leibniz Institut of Polymer Research Dresden, Department Polymer Interfaces, D-01069 Dresden,
13 Germany
14

15 **Abstract**

16 This paper presents an experimental study on the use of zein as a coupling agent in
17 natural fibre composites. Kenaf nonwovens were treated with zein coupling agent,
18 which is a protein extracted from corn. The surface characteristics of untreated and
19 chemically treated kenaf fibres were investigated by FTIR, zeta potential
20 measurements and Energy Dispersive X-Ray Spectroscopy (EDS) mapping.
21 Composites were prepared by compression moulding using nonwovens treated with
22 zein solution. The reinforcing properties of the chemically treated composites were
23 compared with that of untreated composites. The viscoelastic and thermal properties
24 of composites were also determined. Composites containing chemically modified
25 kenaf fibres were found to possess improved mechanical and viscoelastic properties.
26 EDS mapping studies revealed the presence of surface functionalities on treated kenaf
27 fibres.

28
29 Key words: Kenaf fibre, amphiphilic coupling agent, zein, EDS

**Corresponding author*

E-mail: mjohn@csir.co.za, mayajacobkunnel@yahoo.com

Telephone number: ++ 27 41 508 3292

30

31 **INTRODUCTION**

32

33 The use of plant fibre reinforced polymer composites has been the centre of attention
34 of the research community during the last decade (John and Thomas, 2008). The
35 most interesting aspects of natural fibre composites are the high specific properties
36 and the fact that natural fibres are renewable and biodegradable thereby creating a
37 positive environmental impact. Among natural fibre composites, kenaf fibre
38 reinforced composites have found potential applications for mobile phone shells
39 consisting 15–20% kenaf fibres (Iji, 2008). Another example in the automobile
40 industry is the Toyota RAUM, which is equipped with a spare tire cover made of
41 kenaf fibre composites (Anon. 2007).

42

43 The advantages of using polypropylene (PP) as matrix are their low cost and relatively
44 low processing temperature which is essential because of low thermal stability of
45 natural fibres. Amongst eco-compatible polymer composites, special attention has
46 been given to PP composites, due to their added advantage of recyclability. In an
47 interesting study, Srebrenkoska et al, (2008). found that kenaf fibre reinforced
48 polypropylene composites were less sensitive to reprocessing cycles and properties of
49 the composites were unchanged after recycling.

50

51 Most of the studies relating to natural fibre reinforced polypropylene composites use
52 maleic anhydride grafted polypropylene as a compatibilizer (Cantero et al., 2003, Beg
53 and Pickering,2008). Beckmann and Pickering, (2009) investigated the properties of
54 NaOH/Na₂SO₃ treated hemp fibre reinforced polypropylene composites containing

55 4% MaPP. The experimentally obtained tensile strength was found to be one-third of
56 the theoretical prediction. This was attributed to non-axial planar-random orientation
57 of the fibres within the composite. In an earlier study, the authors optimised the
58 concentration of NaOH/Na₂SO₃ treatments on hemp fibres and observed that
59 properties of treated hemp fibres were superior to untreated fibres. Thermogravimetric
60 analysis revealed that thermal stabilities of untreated and treated polypropylene
61 composites were similar (Beckmann and Pickering, 2008)

62

63 In an interesting study, the effect of hybridization of kenaf fibre and wood flour on the
64 dynamic rheological properties of polypropylene composites was investigated by
65 Ghasemi et al. (2009). It was observed that storage modulus of the composites
66 increased with filler loading and the Cole-Cole plots revealed that the relaxation times
67 shifted to higher values with the addition of fillers and the longest relaxation times
68 were related to composites with pure wood flour.

69

70 Shibata et al. (2006) prepared light weight laminate composites from kenaf and
71 polypropylene fibres. The effects of the number of kenaf layers, heating time and
72 kenaf weight fraction on the flexural modulus of the composite specimen were
73 investigated. It was observed that the flexural modulus increased with increasing
74 number of kenaf layers and heating time. The increase of the number of kenaf layers
75 contributed to homogeneous PP dispersion in the composite board. This is because
76 more kenaf layers caused better contact between kenaf and PP and prevented PP
77 fibres from shrinking by heating.

78

79 Natural fibres are hydrophilic in nature as they are lignocellulosic, which contain
80 strongly polarized hydroxyl groups and require chemical modification to increase the
81 compatibility and adhesion between fibres and matrix (John and Anandjiwala, 2008).
82 In most of the studies cited in literature, the chemical modifications employed are
83 synthetic and toxic. It would be ideal if the chemicals used for the modification of
84 natural fibres preserves the biodegradable nature of natural fibres. In this study, we
85 have used zein – protein from corn- as a coupling agent to see its effect on interfacial
86 adhesion in kenaf fibre reinforced polypropylene composites.

87

88 This study focuses on the reinforcement effects of chemically modified and
89 unmodified kenaf polypropylene composites. The viscoelastic and thermal stability of
90 composites have been investigated. The surface characteristics (qualitative) of
91 untreated and treated kenaf fibres have also been examined.

92

93 **2. EXPERIMENTAL**

94 **2.1 Materials**

95 Kenaf fibres were procured from Brits Textiles, South Africa. The fibres received in a
96 bale form were opened and cleaned before processing into nonwovens. As the kenaf
97 fibres still contained a lot of woody pith and other particles, it was subjected to a
98 further opening process in the Trusschler and these fibres were used to produce
99 needle-punched nonwovens. The needle-punched nonwovens from 100% kenaf fibres
100 had an area weight of 110 to 140 g/m². Polypropylene in sheet form (6 mm thickness),
101 with a density of 0.9g/cc and melt flow index of 1.5g /10 min was procured from
102 Ampaglas SA. Zein was obtained from Scientific Polymer Product Company, Ontario,
103 NY. All other chemical reagents used in this study were of analytical grade.

104

105 2.2. Zein modification of kenaf nonwovens

106 Zein belongs to the characteristic class of proteins known as prolamines which occur
107 specifically in cereals. The protein products from corn wet milling are corn gluten
108 meal (CGM) and corn gluten feed (CGF) and zein is obtained as a by-product from
109 corn gluten meal (Momany et al. 2006, Shukla and Cheryan 2001, Wang et al. 2004).

110

111 2 % of zein solution was prepared by mixing with an ethanol/water mixture in the
112 ratio of 80/20. The kenaf nonwovens were immersed in this solution and were
113 allowed to stand for 2 hours. The ethanol/water mixture was drained out and the
114 nonwoven was dried in air and then in an oven at 110°C until completely dry. These
115 nonwovens were used to prepare the modified composites.

116

117 2.3 Preparation of composites

118 Composites were prepared from nonwoven kenaf and polypropylene on the basis of
119 varying fibre content. The kenaf nonwoven mats were cut into small uniform squares
120 (30 cm x 30 cm) and then dried in an air oven at the temperature of 110°C for 7 h.
121 The dried nonwoven mats were placed between weighed polypropylene sheets. This
122 was wrapped in Teflon[®] sheets and sandwiched between two aluminium plates. These
123 two plates were then placed between the two platens of compression moulding press
124 and cured at a pressure of about 35 bar for 20 minutes at 210°C, followed by cooling
125 under pressure for 3 minutes.

126

127

128 3.0 Analysis

129 3.1 Characterization of fibres

130 **FTIR:** Infrared spectra of the untreated and treated kenaf fibres were recorded with an
131 FT-IR spectrometer [Perkin Elmer Spectrum 100 FTIR Spectrometer with an ATR
132 (Attenuated Total Reflectance) sampling accessory]. The spectra were analyzed over
133 the range of 4000 – 650 cm^{-1} .

134 **Electrokinetic Measurements:** Electrokinetic measurements were carried out to
135 determine the zeta-potential (ζ) of fiber surfaces. The electrokinetic analyzer EKA
136 (Anton Paar KG, Graz, Austria) was based on the streaming potential method. An
137 electrolyte solution was forced by an external pressure (p) through a bundle of
138 capillaries (fiber plug). The potential (U) resulting from the motion of ions in the
139 diffuse layer was measured with respect to the applied pressure. The electrokinetic
140 potential or zeta-potential (ζ) was calculated from the measured streaming potential
141 using Smoluchowski's equation ($\Delta U/\Delta p$). During swelling, the ions present in the fiber
142 are incorporated into the swollen layer and influence the surface conductivity. Hence,
143 the calculated zeta potential is considered as an apparent zeta-potential (ζ_{app}). The
144 details of the measuring technique are reported elsewhere (Jacobasch, 1992). By
145 measuring the pH dependence of the zeta-potential, the Brønsted acidity or basicity of
146 solid surfaces can be determined qualitatively.

147 **EDS Mapping:** EDS analysis was carried out using a FEI ESEM-EDS Quanta 200
148 scanning electron microscope. Fibre samples (uncoated) were clamped and sectioned
149 in such a way that a freshly cut surface was presented to the analysing electron beam.
150 The samples were examined at an accelerating voltage of 20kV and a working
151 distance of 6.6 mm. The horizontal field width (HFW) of the image is 746 μm . The

152 detector (*LN2 Si-Li ED*) was set to the energy of the sodium K_{α} electrons and the
153 selected area was repeatedly scanned so that an elemental density map was generated.

154

155 **3.2 Characterization of composites**

156 Tensile and three-point bending tests were carried out using an Instron Universal
157 Testing Machine, model 3369. Tensile testing on rectangular specimens was
158 measured according to ASTM D638 at a crosshead speed of 50 mm/min and a gage
159 length of 50 mm. Flexural testing was carried out in accordance with ASTM D-790, at
160 a crosshead speed of 5mm/min and a span length of 60 mm.

161 Charpy impact strength was measured on an Instron Dynatup, according to ASTM
162 D256. Following test conditions have been used; span length 80 mm and drop weight
163 6.39 kg. During impact, resistive force exerted by the sample on the striker was
164 measured as a function of time.

165 Five specimens were tested for each test and the average data have been reported.

166 Dynamic mechanical analysis was carried out using the Perkin Elmer DMA 8000.
167 Samples of dimensions 50 x 12 x 3 mm were used for testing. The testing temperature
168 ranged from -20°C to 150°C and the experiment was carried out at frequencies
169 0.1,1,10 and 100 Hz. The samples were tested under dual cantilever mode at strain
170 amplitude of 0.05mm.

171 Thermogravimetric (TGA) studies were carried out using a (Pyris 1 model, Perkin
172 Elmer) in an inert atmosphere at a heating rate of 10°C/min. The temperature range
173 used for the analysis is 30 °C to 700 °C.

174

175 **4. Results and Discussion**

176 **4.1 Surface characterization of kenaf nonwovens**

177 4.1.1 FTIR and Zeta potential Studies

178 The amino acid composition in zein (Di Gioia et al. 2000) indicates the presence of
179 both polar and non-polar constituents, the major proportion being glutamine. The
180 FTIR spectra of untreated and zein treated kenaf nonwovens are given in Figure 1 The
181 peaks at 3329 cm^{-1} , 1636 cm^{-1} and 1050 cm^{-1} are assigned to -OH stretching, adsorbed
182 water and -C-O / C-C stretching vibrations respectively. The peak at 1731 cm^{-1}
183 assigned to -CO stretching is more intense in the treated fibre indicating
184 intermolecular attractions. The emergence of new bands on the zein coated kenaf
185 fibres at 1311 cm^{-1} and 1418 cm^{-1} assigned to C-N stretching are indicative of the fact
186 zein coating has modified the fibre surface.

187

188 The electrokinetic measurements were used to characterize the acid-base properties of
189 chemically modified fibres. Figure 2 presents the pH dependence of the apparent zeta
190 potential. It can be seen that there is a significant difference between untreated and
191 zein treated kenaf nonwovens. For the untreated kenaf nonwovens, the iso-electric
192 point (IEP, pH where zeta potential is zero) is found at $\text{pH} = 2.9$. The Stern theory of
193 electrochemical double layer (Stern, 1924) relates this point to the number of
194 Bronsted acid surface sites. The increase of pH lowers the zeta potential indicating the
195 gradual loss of protonated surface groups (Poathan et al. 2006). The negative zeta
196 potential also suggests the dissociation of Bronsted acid surface sites. The zeta
197 potential versus pH curve has a shape that is typical for surfaces with hydrophilic
198 character. It can be observed that there are two distinct plateau phases for the
199 untreated kenaf fibre- first plateau starts at $\text{pH} \sim 3.5$ and second plateau starts at pH
200 ~ 6.2 . These phases indicate the two different surface charging mechanisms, the
201 dissociation of (Bronsted acid groups) followed by adsorption of OH^- ions on the fibre

202 surface. The IEP of the treated kenaf fibre shifts to higher pH values indicating that
203 the polarity of the fibres has changed.

204

205 **4.1.2 ESEM and EDS mapping**

206 Figure 3 presents the corresponding density map of EDS spectrum of zein coated
207 kenaf sample and the quantitative elemental analysis of treated kenaf fibres. Natural
208 fibres contain cellulose, hemicellulose, lignin and waxes. As a result, it contains
209 organic matter as carbon and oxygen. Inorganic elements like silicon can also be
210 present. The non-cellulosic constituents in natural fibres include proteins, amino acids
211 and other nitrogen containing compounds. Most of the nitrogenous materials occur in
212 the primary cell wall as well as the lumen of the fibre as protoplasmic residue (Lewin,
213 2007). This explains the presence of nitrogen in the untreated kenaf fibres. It can be
214 observed that there is an increase in concentration of nitrogen and sulphur for the
215 treated fibre indicating that there is presence of zein on the surface of fibres. EDS
216 mapping also revealed the distribution patterns of nitrogen and sulphur on the zein
217 coated kenaf fibres. The distribution of sulphur seems to be uneven and random but a
218 uniform and higher concentration of nitrogen was detected.

219

220

221 **4.2 Effect of zein modification**

222 Figures 4 and 5 exhibit the tensile and flexural properties of untreated and zein
223 modified kenaf composites at 30% fibre loading. It can be seen that after modification
224 flexural strength increased by 7 % while tensile strength did not register a significant
225 increase. It may be noted that the authors had observed a higher percentage of
226 increment in the case of zein treated flax-PP composites (John and Anandjiwala,

227 2009). This can be attributed to the physical nature of kenaf fibres. Kenaf stem
228 contains two types of fibre, bast fibre and woody core fibre. The bast fibres need to be
229 separated from the woody core fibre before being used in composites (Lips, 2009). In
230 the present case it was observed that the bast fibres contained a lot of woody particles
231 and pith that were not completely removed even though the fibres were subjected to
232 intensive cleaning process. As a result it is most probable that zein solution was not
233 able to coat the kenaf fibres uniformly.

234

235 Impact strength (Figure 4) is seen to decrease due to modification of kenaf fibres with
236 zein protein. The energy dissipation mechanisms operating during impact fracture are
237 matrix and fibre fracture, fibre–matrix debonding and fibre pull out. Fibre fracture
238 dissipates lesser energy compared to fibre pull out. The main failure mechanism in
239 these composites is fibre fracture (as there is not significant interfacial adhesion),
240 resulting in lower energy dissipation and hence impact strength decreases.

241

242 Zein is neither soluble in pure water nor in alcohol but requires a high percentage of
243 alcohol-aqueous system for dispersion. There are mainly four types of zein ($\alpha, \beta, \gamma, \delta$)
244 which are classified according to their solubility properties. The isoform α -zein, which
245 accounts for ~85% of zein in the corn kernel, has a unique amino acid sequence
246 containing more than 50% nonpolar amino acids. The secondary and tertiary structure
247 of zein was reported as having a possible configuration containing 9 or 10 α -helix
248 segments folded upon each other in a nonparallel fashion. According to the model
249 proposed by Argos et al (1982) helical segments are arranged in a ring of "pencils"
250 held together, side-by-side, by hydrogen bonds and linked at each end by glutamine-
251 rich turns or loops. The exterior of the helical segments forming the lateral faces have

252 a hydrophobic character, whereas the top and bottom surfaces containing the
253 glutamine-rich loops are hydrophilic. Therefore, zein is amphiphilic in nature having
254 affinity for both polar and non-polar groups. This characteristic allows it to bind itself
255 between the polar kenaf nonwovens and non-polar matrix results in enhanced
256 mechanical properties.

257

258 **4.3 Dynamic mechanical analysis**

259 **4.3.1 Effect of fibre loading**

260 **4.3.1.1 Storage Modulus**

261 Storage modulus (E') provides valuable input into the stiffness of composites and
262 measures the elastic response of a material. The variation of storage modulus with
263 temperature (measured at 1 Hz) at different kenaf fibre loading at is given in Figure 6.
264 It can be seen that storage modulus increases with increasing kenaf content at all
265 temperatures when compared to the polypropylene. When fibres are incorporated in
266 the polypropylene matrix, the stiffness of the composite increases resulting in high
267 storage modulus. Also, the addition of fibres allows effective stress transfer at the
268 interface, which consequently increases the storage modulus.

269

270 **4.4.1.2 Loss Modulus and damping properties**

271 Loss modulus is a measure of the viscous response of a material. Table 1 shows that
272 loss modulus (at 20°C) increases with increase in fibre loading. The increase in loss
273 modulus is attributed to the increase in energy absorption caused by the addition of
274 fibres. It can be observed that upon incorporation of kenaf nonwovens, $\tan \delta$
275 decreases. Incorporation of nonwovens acted as barriers to the mobility of polymer
276 chains, leading to lower degrees of molecular motion and hence lowers damping

277 characteristics. The glass transition temperature does not seem to have a significant
278 co-relation with fibre loading.

279

280 **4.4.2. Effect of zein coating**

281 **4.4.2.1. Storage Modulus and $\tan \delta$**

282 The variation of storage modulus and $\tan \delta$ with zein coating for 30% kenaf fibre
283 composites is given in Figure 7 (a) and (b). It can be observed that storage modulus of
284 the treated composites shows an increase. This can be attributed to the better
285 reinforcing effects which increase the thermal and mechanical stability of the material
286 at higher temperatures. It must be noted that the increment is prominent between 60 –
287 80 °C temperature ranges. In Figure 7 (b) the position of β -relaxation was found to be
288 shifted to higher temperatures and magnitude of $\tan \delta$ was seen to decrease for
289 chemically modified composites. This was attributed to a more compact structure in
290 treated composites leading to further hindrance of molecular motions which
291 consequently reduced $\tan \delta$.

292

293 **4.4.3 Thermal Analysis.**

294 **4.4.3.1 Effect of fibre loading**

295 Table 1 presents the peak temperatures obtained from derivative thermograms of all
296 the composites. The degradation of polypropylene is a one step process and the major
297 peak is observed around 501.8°C. In the composite two peaks were obtained; a minor
298 peak at at 410°C due to hemicellulose and α -cellulose degradation and the major peak
299 at 524.1 °C indicating higher thermal stability for the composites. The addition of
300 kenaf nonwovens results in an increase of degradation temperatures which could be
301 attributed to consolidation effects (Araujo et al., 2007). On comparing the stability of

302 the untreated and treated composites it was seen that thermal stability of composites
303 containing zein coated flax nonwovens decreased when compared to the untreated
304 sample.

305

306

307 **5. CONCLUSIONS**

308

309 This study focused on the effect of using a chemical modification that preserves the
310 renewable and biodegradable character of natural fibres. Zein coating of kenaf
311 nonwovens was found to enhance the flexural and viscoelastic properties of
312 composites. The storage modulus increased for composites containing zein coated
313 kenaf fibres indicating increased stiffness in treated composites. Chemical
314 modification of kenaf nonwovens resulted in a slight decrease of thermal stability.
315 Surface characterization of raw and chemically modified kenaf nonwovens revealed
316 the presence of surface functionalities. Energy dispersive X-ray analysis confirmed
317 the qualitative and quantitative evidence of nitrogen and sulphur on the surface of the
318 zein coated fibres.

319

320

321

322

323

324

325

326

327 **CAPTIONS TO FIGURES**

328

329 Figure 1: FTIR spectra of untreated and zein coated kenaf fibre

330 Figure 2: Zeta potential measurements of raw and zein coated fibres

331 Figure 3: Density map of EDS-spectrum of zein coated kenaf sample

332 Figure 4: Variation in tensile, flexural and impact strength of untreated and treated
333 composites334 Figure 5: Variation of tensile and flexural modulus of untreated and treated
335 composites

336 Figure 6: Variation in storage modulus with temperature as a function of fibre loading

337 Figure 7: Variation in storage modulus and tan delta of untreated and treated
338 composites

339

340

341

342

343

344

345

346

347

348

349

350

351

352

353 **References**

- 354 Anonymous, (2007). Bioplastics in automotive applications. *Bioplastics Mag* 2,14–8.
- 355 Araujo, J.R., Waldman, W.R., De Paoli, M.A.,(2008). Thermal properties of high
356 density polyethylene composites with natural fibres: Coupling agent effect. *Polymer*
357 *Degradation and Stability*, 93, 1770-1775
- 358 Argos, P., Pedersen, K.,Marks, M.D., & Larkins, B.A., (1982). A Structural Model for
359 Maize Zein Proteins. *Journal of Biological Chemistry*, 257, 17, 9984-9990.
- 360 Beckmann, G.W., Pickering, K.L., (2008) Engineering and evaluation of hemp fibre
361 reinforced polypropylene composites: Fibre treatment and matrix modification,
362 *Composites Part A: Applied Science and Manufacturing*, 39,979-988
- 363 Beckmann, G.W., Pickering, K.L., (2009) Engineering and evaluation of hemp fibre
364 reinforced polypropylene composites: Micro-mechanics and strength prediction
365 modelling, *Composites Part A: Applied Science and Manufacturing*, 40, 210-217
- 366 Beg M.D.H., Pickering K.L., (2008) Reprocessing of wood fibre reinforced
367 polypropylene composites. Part I: Effects on physical and mechanical properties,
368 *Composites Part A: Applied Science and Manufacturing*, 39, 1091-1100
- 369 Cantero, G., Arbeliaz, A., Lano-Ponte, R., Mondragon I., (2003) Effects of fibre
370 treatment on wettability and mechanical behaviour of flax/polypropylene composites.
371 *Composites Science and Technology*, 63, 1247-1254
- 372 Di Gioia, L.,Cuq, B.,Guilbert, S., (2000). Mechanical and water barrier properties of corn-
373 protein-based biodegradable plastics. *Journal of Materials Research*, 15, 2612-2619.
- 374 Ghas Ghasemi, I., Azizi, H., Naeimian, N., (2009). Rheological behaviour of
375 Polypropylene/Kenaf Fibre/Wood Flour Hybrid Composite. *Iranian Polymer Journal*, 17,191-
376 198


- 377 Iji, M., (2008). Highly functional bioplastics used for durable products. In: The Netherlands
378 Science and Technology (Organizer and Editor); Innovative Technologies in Bio-Based
379 Economy. Wageningen, The Netherlands, [<http://www.twanetwork.nl>].
- 380 Jacobasch, H.J., Simon, F., Werner, C., Bellmann, C., (1992). Technisches Messen.
381 Electrokinetic measuring methods Principles and applications. 89, 1615-1622.
- 382 John, M.J., Anandjiwala, R.D., (2009). Chemical modification of flax reinforced
383 polypropylene composites. Composites Part A, 40, 442–448.
- 384 John, M.J., Anandjiwala, R.D., (2008). Recent developments in chemical modification and
385 characterization of natural fiber reinforced composites. Polymer Composites, 29, 187 – 207.
- 386 John, M.J., Thomas, S., (2008). Biofibres and Biocomposites. Carbohydrate Polymers, 71,
387 343–364.
- 388 Lewin, M., (2007) Handbook of Fibre Chemistry. 3rd Edition, CRC Press, Taylor and Francis
389 Group
- 390 Lips, S.J.J., Iniguez de Heredia, G.M., Op den Kamp, R.G.M., van Dam, J.E.G., (2009).
391 Water absorption characteristics of kenaf core to use as animal bedding material. Industrial
392 Crops and Products, 2, 73–79.
- 393 Momany, F.A., Sessa, D.J., Lawton, J.W., Gordon, W., Selling, G.W., Hamaker, S.A.H., &
394 Willet, J.L., (2006). Structural Characterization of α -Zein. Journal of Agricultural Food and
395 Chemistry, 54, 543-547.
- 396 Pothan, L.A., Simon, F., Spange, S., Thomas, S., (2006). XPS Studies of Chemically
397 Modified Banana Fibers. Biomacromolecules, 7, 892-898.
- 398 Shibata, S., Cao, Y., Fukumoto, I., (2006) Lightweight laminate composites made from kenaf
399 and polypropylene fibres. Polymer Testing, 25, 142-148
- 400 Shukla, R., Cheryan, M., (2001). Zein: The industrial protein from corn. Industrial Crops and
401 Products, 13, 171–192.
- 402 Srebrenkoska, V., Gaceva, G.B., Avella, M., Errico, M.E., Gentile, G., (2008). Recycling of
403 polypropylene-based eco-composites. Polymer International, 57, 1252–1257.


- 404 Stern, O.Z., (1924). Zeitschrift fuer Elektrochemie und Angewandte Physikalische Chemie.
405 The theory of the electrolytic double-layer 30 508-516.
- 406 Wang, Q., Wang, J.-F., Geil, P.H., Padua, G.W., (2004). Zein Adsorption to Hydrophilic and
407 Hydrophobic Surfaces Investigated by Surface Plasmon Resonance. Biomacromolecules, 5,
408 1356–1361.
- 409



Accepted Manuscript

Table 1: Loss modulus, T_g and peak temperatures of composites

	E'' [Pa] 20 °C	$\tan \delta$	T_g [° C]	Temperatures [°C]	
				Peak I	Peak II
PP	5.23×10^7	0.1280	1.2	-	501.8
20	5.78×10^7	0.1275	2.6	411.37	524.07
30	6.51×10^7	0.1247	0.61	415.60	535.5
40	6.81×10^7	0.1002	4.8	421.84	533.4
2% zein	7.434×10^7	0.1183	1.4	380.10	519.4

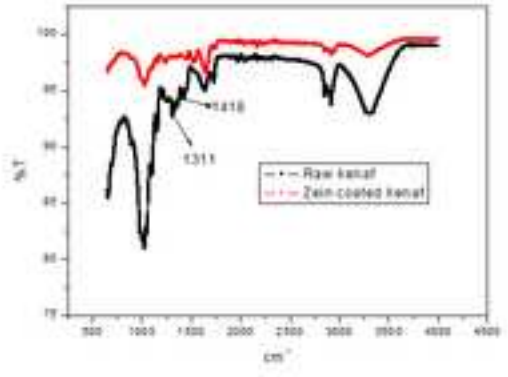


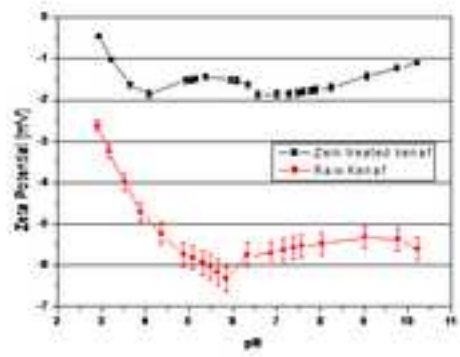


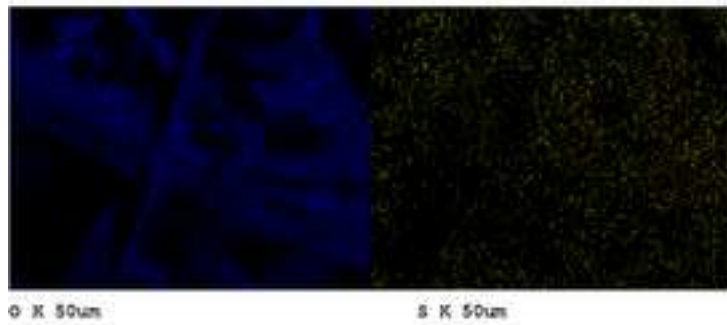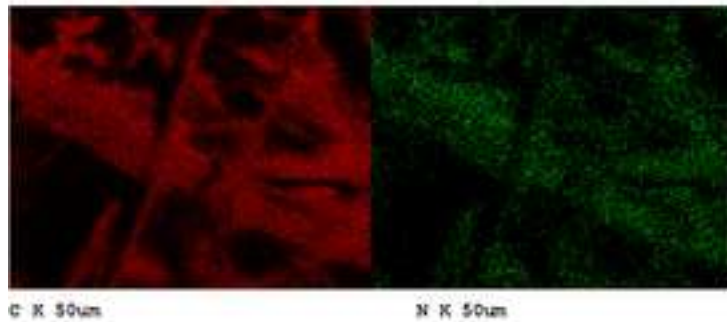



Fibres	Element (Wt %)			
	C	O	N	S
Untreated kenaf fibre	62.5	35.27	1.01	-
Zein treated kenaf fibre	55.5	25.1	18.6	0.6

Figure 3

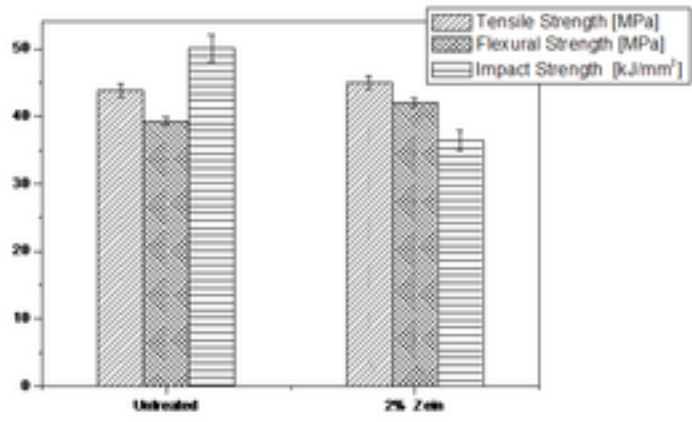


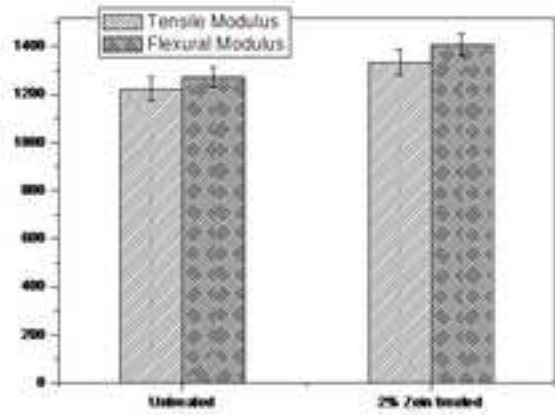

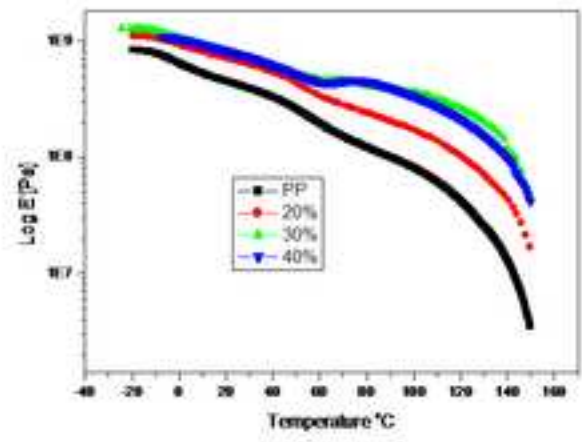

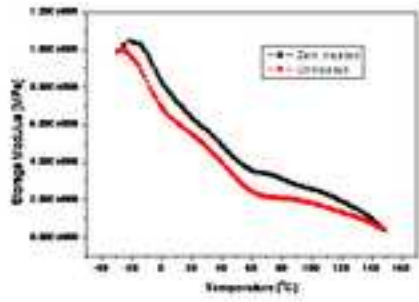

a

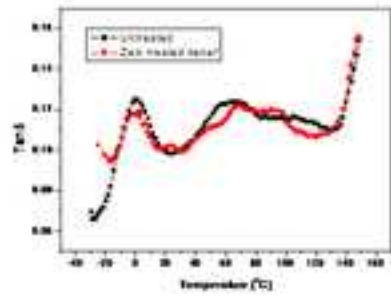

b